

Control of fine grain structures and strengthening-toughening mechanisms in magnesium alloys fabricated by wire-arc directed energy deposition

Wei Liu¹, *Hai-long Jia^{1,2}, Yi-hang Yang¹, Min Zha¹, Pin-kui Ma¹, and Hui-yuan Wang^{1,2}

1. Key Laboratory of Automobile Materials of Ministry of Education & School of Materials Science and Engineering, Nanling Campus, Jilin University, No. 5988 Renmin Street, Changchun, 130025, China

2. International Center of Future Science, Jilin University, Changchun, 130012, China

*Corresponding address: e-mail: jiahailong@jlu.edu.cn

Copyright ©2025 17th Asian Foundry Congress, Foundry Institution of Chinese Mechanical Engineering Society

Abstract: Wire-arc directed energy deposition (WA-DED) has attracted considerable attention for the fabrication of magnesium (Mg) alloys due to its high efficiency, low cost, and rapid prototyping capability for complex components. However, the inherent rapid solidification and complex thermal cycling associated with WA-DED often result in coarse columnar grains and pronounced mechanical anisotropy, which severely limiting its application potential. In this study, a novel spiral oscillation (SO) strategy is implemented during WA-DED AZ31 Mg alloy to refine the microstructure, reduce mechanical anisotropy, and achieve a strength-ductility synergy. Specifically, the yield strength (YS), ultimate tensile strength (UTS) and elongation (EL) are increased by 9.7%, 20.8% and 80%, respectively. These improvements by the SO strategy are primarily attributed to the promotion of columnar-to-equiaxed transformation (CET), a 74.2% reduction in maximum texture intensity, and a more uniform distribution of second-phase particles. Second-phase particles are primarily composed of $Al_8 Mn_5$ and $Al_8 Mn_4 Y$. This study demonstrates a novel strategy for microstructural control aimed at improving the performance of WA-DED AZ31 Mg alloy components.

Keywords: Magnesium alloy; Wire arc directed energy deposition; Spiral oscillation; isotropy; strength-ductility synergy

1 Introduction

Magnesium alloys represent the lightest class of engineering structural materials, with a density of $\sim 1.74 \text{ g/cm}^3$ —approximately 65% that of aluminum, 40% of titanium, and 25% of steel^[1,2]. Although the absolute tensile strength of Mg alloys is generally lower than of high-strength steels or certain aluminum alloys, their exceptionally low density results in a remarkably high specific strength and specific stiffness, which can exceed those of some aluminum alloys and steels. Furthermore, Mg alloys have excellent electromagnetic shielding capabilities and biodegradability, making them ideal for lightweight structural applications with significant potential in automotive, military equipment, aerospace and other fields^[3-5]. However, conventional fabrication

methods for Mg alloys—such as casting, forging, extrusion, and rolling—are often constrained by mold limitations. These processes are susceptible to metallurgical defects like porosity and generally struggle to directly form complex components. Moreover, the inherent hexagonal close-packed (HCP) crystal structure of Mg alloys results in low plasticity and poor formability at room temperature, which further limits the application of Mg alloys^[6,7]. Therefore, there is an urgent need to develop advanced manufacturing techniques capable of integrating complex geometries while mitigating the limitations of traditional processing routes.

Additive manufacturing (AM) is an emerging fabrication technique that builds components layer by layer along a predefined path, enabling the rapid

prototyping of complex geometries^[8]. Unlike traditional subtractive manufacturing methods, AM is not constrained by shape limitations, offering substantial potential for the fabrication of complex Mg alloy components. According to the type of heat source and raw materials, the most commonly used metal AM processes are categorized into three types: laser powder bed fusion (L-PBF), laser directed energy deposition (L-DED), and wire arc additive manufacturing (WAAM, also called wire arc directed energy deposition, WA-DED)^[9]. However, the high laser reflectivity of Mg alloys, coupled with the high flammability and explosiveness of Mg alloy powders, introduces significant safety concerns in industrial applications^[10]. These safety concerns severely limit the application of L-PBF and L-DED for Mg alloys. In contrast, WA-DED employs Mg alloy wire as raw material and an electric arc as the heat source, effectively eliminating powder-related safety hazards. This intrinsic safety advantage makes WA-DED a highly promising technology for the additive manufacturing of Mg alloys.

The primary process parameters WA-DED include deposition current and deposition speed, both of which significantly affect the geometric formability and overall quality of deposited components. Previous studies indicate that a high deposition speed combined with a low deposition current can result in discontinuous deposits due to insufficient heat input and incomplete wire melting. Conversely, a low deposition speed combined with a high deposition current can lead to excessive material accumulation due to the slower movement of the deposition head^[11]. Therefore, the optimization of these process parameters is essential to achieving high-quality deposition. In addition to improving deposition quality, optimized process parameters can promote grain refinement and reduced texture intensity^[12]. However, grain coarsening is frequently observed with increasing build heights. This phenomenon is primarily attributed to the decreased heat dissipation efficiency and hindered thermal diffusion at greater heights, caused by cumulative heat input inherent to the layer-by-layer deposition process^[13]. The variation in thermal cycling and heat accumulation at different build heights inevitably results in heterogeneous microstructural evolution throughout the component. Consequently, this microstructural heterogeneity leads to variations in mechanical properties. As reported in previous studies^[6,14], AZ31 Mg alloy components fabricated via WA-DED commonly exhibit coarse columnar grain structures, which result in pronounced mechanical anisotropy and limit their broader industrial applicability.

In WA-DED Mg alloys, the primary methods currently employed for grain refinement to enhance mechanical properties include the application of external energy fields (e.g., ultrasonic vibration^[15], cryogenic cooling^[12], water cooling^[14], etc.), the introduction of localized plastic deformation (e.g., via laser shock peening^[16]), and the addition of heterogeneous nucleation particles^[17]. Although these methods have demonstrated effectiveness in grain refinement and performance improvement, they are often limited by operational complexity, requiring additional specialized equipment.

Heat source oscillation has been widely applied in AM processes involving laser or laser-arc hybrid heat sources to promote grain refinement and enhance mechanical properties^[18,19]. However, in the context of WA-DED for Mg alloys, the feasibility of employing oscillation strategies—particularly through modifications of the deposition path—to influence microstructural evolution and mechanical performance remains insufficiently explored and warrants further investigation.

In this study, a spiral oscillation (SO) deposition strategy is introduced to enhance the conventional straight-line (SL) deposition approach for WA-DED AZ31 Mg alloy. This strategy is designed to refine microstructures and improve mechanical properties of deposited components. The effects of SO strategy on grain size and morphology, second-phase distribution and composition, and mechanical performance have been systematically investigated through electron backscatter diffraction (EBSD) and scanning electron microscopy (SEM) characterization. This work presents a novel processing route for WA-DED AZ31 Mg alloy, enabling grain refinement and the fabrication of high-performance Mg alloy components with isotropic mechanical properties.

2 Experimental

2.1 Material preparation

In this work, AZ31 Mg alloy wire (wt.%, 2.6 Al, 0.6 Zn, 0.5 Mn, 0.5 Sn, 0.01 Y) with a diameter of 1.2 mm was used as the raw material. Deposition was carried out on rolled AZ31 Mg alloy substrates with dimensions of 200 × 30 × 4 mm³ (L × W × H) using the cold metal transfer wire-arc additive manufacturing (CMT-WAAM) system. A schematic of the deposition process is shown in Fig. 1(a). Two deposition paths were employed: straight-line (SL) and spiral oscillation (SO), as illustrated in Fig. 1(b). The key process parameters included a deposition current of 110 A and a deposition speed of 5 mm/s. For SO deposition, an oscillation

amplitude of 4 mm and wavelength of 3 mm were applied. High-purity argon gas (99.99%) was used as the shielding atmosphere at a flow rate of 18–20 L/min. To ensure thermal consistency between layers, inter-layer cooling to 50 °C was conducted before each subsequent deposition. Thin-walled components comprising ten layers were fabricated using these parameters with bidirectional deposition.

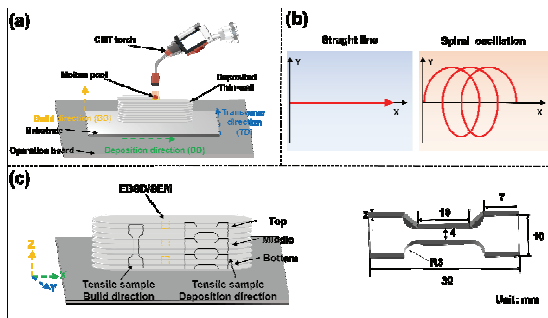


Fig. 1. Schematic of the experimental process for WA-DED AZ31 Mg alloy components: (a) deposition process; (b) deposition path; (c) position and size of the sample.

2.2 Material preparation

Microstructural characterization was performed using a Zeiss Sigma 500 scanning electron microscope (SEM) equipped with an Oxford Instruments NordlysNano AZtec electron backscatter diffraction (EBSD) detector and an X-MaxN AZtec energy dispersive spectroscopy (EDS) system. Sample cutting locations are shown in Fig. 1(c). For EBSD analysis, samples were electrolytically polished at 20 V for 40–45 s in a solution (800 mL ethanol, 100 mL propanol, 18.5 mL distilled water, 10 g hydroxyquinoline, 75 g citric acid, 41.5 g sodium thiocyanate, 15 mL perchloric acid). The EBSD data acquisition step size was set to be 5 μ m and the acquired data were analyzed using Channel 5 software. Tensile sample geometries and extraction locations are also shown in Fig. 1(c). Room-temperature tensile tests were carried out using a Shimadzu AGS-X universal testing machine at a constant crosshead speed of 0.6 mm/min.

3 Results and discussion

3.1 Mechanical properties

Fig. 2(a) presents statistical histograms comparing mechanical properties of SL and SO deposited components. As shown in Fig. 2(a), mechanical properties of components deposited with the SO strategy are significantly improved. Specifically, the SL component shows maximum yield strength (YS), ultimate tensile strength (UTS), and elongation (EL) values of 92 MPa, 192 MPa, and 9% along the building

direction (BD) and deposition direction (DD), respectively, whereas the SO component exhibits minimum values of 101 MPa, 232 MPa, and 16.2% along the same directions. Compared to the SL component, the SO strategy resulted in improvements of at least 9.7%, 20.8%, and 80% in YS, UTS, and EL, respectively. These results demonstrate that the SO strategy effectively enhances mechanical performance and achieves a synergistic improvement in both strength and ductility.

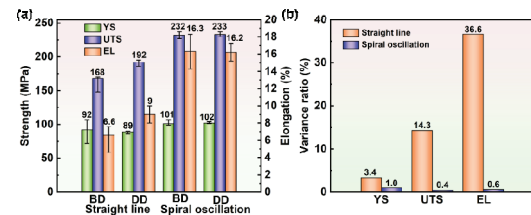


Fig. 2. Room temperature tensile property statistics: (a) performance statistics histogram; (b) histogram showing the rate of difference in performance comparison between BD and DD.

It is worth noting that the SL component exhibit pronounced mechanical anisotropy between BD and DD, whereas the SO component shows markedly improved isotropy. To facilitate a more intuitive comparison, the variance rates of mechanical properties between BD and DD have been calculated, as shown in Fig. 2(b). As shown, the variance rates of YS, UTS, and EL between BD and DD decrease from 3.4%, 14.3%, and 36.6% in SL component to 1.0%, 0.4%, and 0.6% in SO component, respectively. These results clearly demonstrate that the SO strategy significantly enhances the isotropy of mechanical properties in WA-DED AZ31 Mg alloy component.

3.2 Grain morphology and texture analysis

EBSD analyses have been performed on two deposited components (SL and SO) to investigate the effects of SO strategy on grain morphology and size distribution, as shown in Figs. 3 and 4, respectively. As illustrated in Fig. 3, grains at different locations of the SL component exhibits a microstructure comprising coarse columnar grains and fine grains, with a significant higher percentage of columnar grains. The average grain sizes of bottom, middle, and top regions are 84.8 μ m, 93.7 μ m and 99.1 μ m, respectively. It indicates a progressive increase in grain size with deposition heights. Furthermore, comparative analysis of EBSD IPF maps from bottom to top regions further reveals a distinct evolution in columnar grain morphology: the bottom region near the substrate contains finer grains, while the top region is dominated by coarser and fewer grains. This

grain coarsening with increasing build heights is primarily attributed to changes in heat dissipation efficiency during the layer-by-layer deposition process^[13]. Near the substrate, direct contact enables efficient heat extraction and rapid cooling, thereby restricting grain growth and promoting the formation of fine grains. As the deposition height increases, the thermal path becomes longer and less efficient, reducing the cooling rate and allowing grains to grow more extensively. As a result, the upper regions of the SL component develop a microstructure dominated by coarse columnar grains.

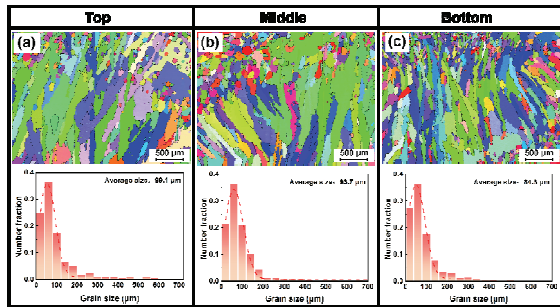


Fig. 3. IPF maps and grain size distribution histograms of different positions in SL component: (a) top; (b) middle; (c) bottom.

As shown in Fig. 4, the microstructure of the SO component comprises a mixture of fine columnar grains and fine equiaxed grains uniformly distributed across all regions. In contrast to the SL component, the SO strategy significantly increases the proportion of equiaxed grains. The average grain sizes in the bottom, middle, and top regions of the SO component are 69.8 μm , 71.0 μm , and 74.2 μm , respectively. It exhibits a similar trend of increasing grain sizes with build heights. Additionally, EBSD IPF maps demonstrate a progressive reduction in the fraction of coarse columnar grains along the deposition height from the top to bottom regions. Similar to the SL condition, this microstructural evolution is governed by the progressive reduction in heat dissipation efficiency with increasing deposition heights^[13].

Compared to the SL strategy, the SO strategy induces a clear microstructural transition from coarse columnar grains to fine equiaxed grains. Significant grain refinement is achieved in the bottom, middle, and top regions, with average grain size reductions of 15.0 μm (17.7%), 22.7 μm (24.2%), and 24.9 μm (25.1%), respectively. These results confirm that the SO strategy effectively refines the grain structure and promotes columnar-to-equiaxed transformation (CET). Grain refinement increases the density of grain boundaries, which act as barriers to dislocation motion and thus enhance the yield strength via the Hall-Petch relationship^[20,21]. Furthermore, while grain boundaries in

coarse columnar structures can serve as preferential pathways for rapid crack propagation, the transition to equiaxed grains mitigates this tendency, thereby reducing susceptibility to premature fracture^[17]. The uniform morphology of equiaxed grains also promotes uniform plastic deformation under applied loading. Collectively, these microstructural modifications—including grain refinement, CET, and morphological homogenization—contribute to the substantial improvements in mechanical properties observed in the SO component.

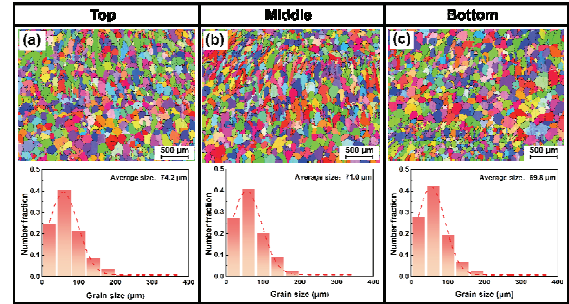


Fig. 4. IPF maps and grain size distribution histograms of different positions in SO component: (a) top; (b) middle; (c) bottom.

Pole figures for different positions of SL and SO components are shown in Figs. 5 and 6, respectively. As illustrated in Fig. 5, the maximum texture intensity in the SL component decreases progressively from 22.4 mrd at the top to 11.5 mrd in the middle and 9.3 mrd at the bottom. This trend is attributed to the microstructural evolution along the build height—from a small number of large columnar grains in the upper regions to a higher density of smaller columnar grains near the substrate.

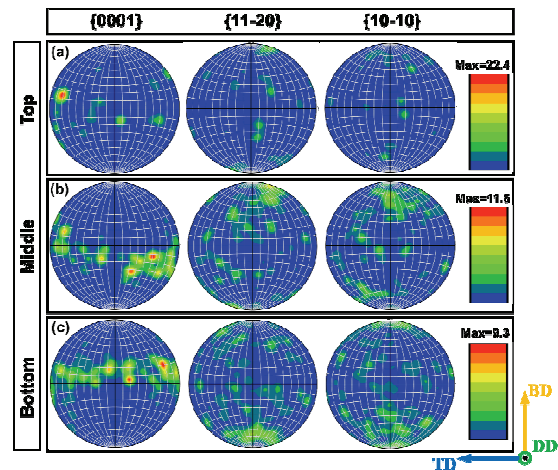


Fig. 5. Pole figures of different positions in SL component: (a) top; (b) middle; (c) bottom.

Fig. 6 shows that the maximum texture intensity in the SO component decreases progressively from 3.1 mrd at the top to 2.9 mrd in the middle and 2.4 mrd at the bottom. Compared to the SL component,

texture intensities in the SO component are significantly reduced. Specifically, maximum texture intensities at the top, middle, and bottom regions are decreased by 19.3 mrd (86.2%), 8.6 mrd (74.7%), and 6.9 mrd (74.2%), respectively. Furthermore, grains in the SO component exhibit predominantly random orientations, which is beneficial for reducing mechanical anisotropy of deposited components.

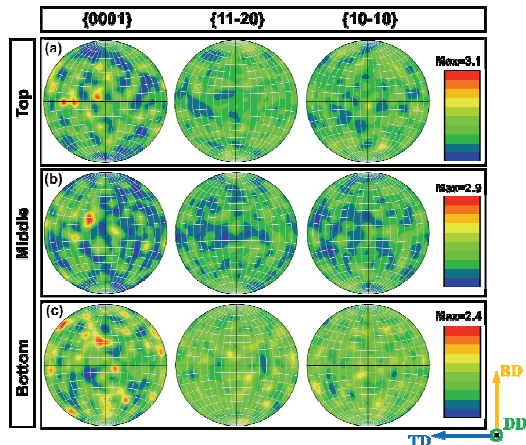


Fig. 6. Pole figures of different positions in SO component: (a) top; (b) middle; (c) bottom.

3.3 Second-phase evolution

Fig. 7 presents SEM images of different regions in both SL and SO components. It can be observed that, for both deposition strategies, the size of second-phase particles increases progressively from bottom to top, with this trend being more pronounced in the SL component. This phenomenon is primarily attributed to the reduction in heat dissipation efficiency with increasing build heights. Furthermore, the second-phase distribution in the SO component is significantly more uniform compared to that in the SL component. The SO strategy facilitates this uniformity by disrupting the localized accumulation of second-phase particles, which helps to mitigate stress concentrations that typically act as sites for crack initiation. As a result, the more homogeneous second-phase distribution achieved by the SO strategy contributes to improved ductility and overall mechanical performance.

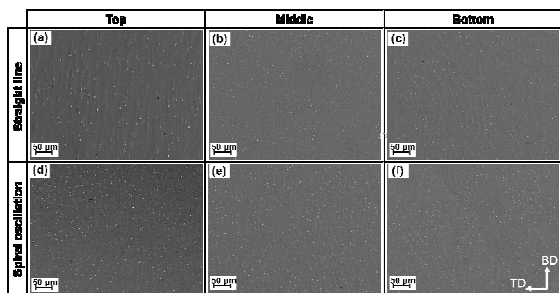


Fig. 7. SEM images of different positions in the (a-c) SL component

and (d-f) SO component: (a, d) top; (b, e) middle; (c, f) bottom.

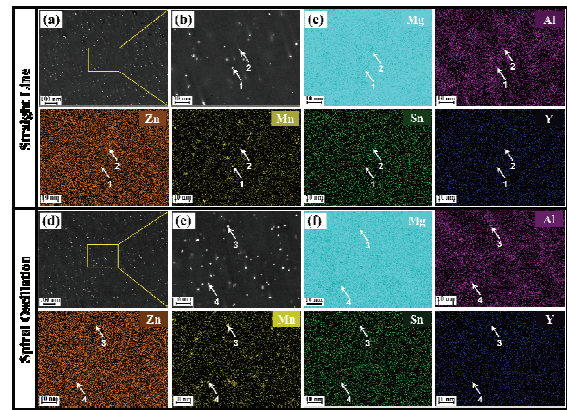


Fig. 8. SEM and EDS images of the middle region of the (a-c) SL component and (d-f) SO component: (a, d) SEM; (b, c) locally magnified images corresponding to Figs. a and d, respectively; (c, f) EDS images corresponding to Figs. b and c, respectively.

Table 1. Composition of second-phases (at.%), corresponding to points in Fig. 8.

Point	Al	Mn	Zn	Sn	Y	Mg
1	4.65	2.25	0.16	0.03	0.01	Bal.
2	2.66	0.96	0.01	0.01	0.21	Bal.
3	2.47	1.24	0.16	0.02	0.01	Bal.
4	3.39	1.03	0.01	0.01	0.27	Bal.

Fig. 8 presents EDS analyses of middle regions in SL and SO components. From Fig. 8, it can be seen that second-phase particles are primarily enriched in Al and Mn elements. Point analyses of the second-phases in SL and SO components reveal that atomic ratios of points 1 and 3 are similar to those of the Al_8Mn_5 phase, while atomic ratios of points 2 and 4 are similar to those of the Al_8Mn_4Y phase. Importantly, the SO strategy alters the distribution of second-phase particles—promoting a more uniform dispersion—without changing their chemical composition. This suggests that improved mechanical properties observed in the SO component are attributed to changes in second-phase distribution and morphology, rather than the second-phase type.

4 Conclusions

To promote the columnar-to-equiaxed transition (CET), reduce mechanical anisotropy, and achieve simultaneous strength-ductility enhancement in WA-DED AZ31 Mg alloy, a SO strategy has been implemented during deposition. Microstructures of SL and SO components have been systematically investigated, and the effects of SO on grain morphology

and size, texture intensity, second-phase distribution/composition and mechanical properties have been comprehensively analyzed. Main conclusions are summarized as follows:

(1) The SO strategy significantly improves the mechanical performance of WA-DED AZ31 Mg alloy components, achieving a synergistic enhancement in both strength and ductility while reducing mechanical anisotropy. The YS, UTS, and EL of SL component are 92 MPa, 192 MPa, and 9%, respectively. In comparison, the SO component exhibits improved values of 101 MPa (YS), 232 MPa (UTS), and 16.2% (EL), representing increases of 9.7%, 20.8%, and 80%, respectively. Furthermore, the variance rates of YS, UTS, and EL between BD and DD decrease markedly from 3.4%, 14.3%, and 36.6% for SL component to 1.0%, 0.4%, and 0.6% for SO component, indicating improved isotropy in mechanical properties.

(2) The SO strategy promotes CET, refining grains and reducing the texture intensity. Specifically, the microstructure of SL component mainly consists of coarse columnar grains with an average grain size of $93.7 \mu\text{m}$, while the SO component exhibits predominantly fine equiaxed grains with a reduced average grain size of $71.0 \mu\text{m}$, corresponding to a 24.2% reduction ($22.7 \mu\text{m}$). Additionally, the maximum texture intensity is substantially decreased from 11.5 mrd in SL component to 2.9 mrd in SO component, with the latter showing more randomized grain orientations—favorable for enhancing isotropic mechanical behavior.

(3) The second-phase of both SL and SO components has a tendency to increase in size with increasing deposition heights. This is more pronounced in the SL component, which is mainly related to the change in heat dissipation conditions. The SO strategy promotes a more uniform distribution of second-phase particles, mitigating stress concentration and improving ductility. However, the chemical composition of second-phases remains unchanged. EDS analyses confirm that second-phase particles in both cases are Al_6Mn_5 and $\text{Al}_6\text{Mn}_4\text{Y}$.

Acknowledgments

This work was funded by National Natural Science Foundation of China (Nos. 52334010 and 52001133), Graduate Student Research Innovation Capability Enhancement Project of Jilin Province (No. JJKH20250101BS) and Jilin Scientific and

Technological Development Program (No. 20220301026GX).

Conflicts of interest:

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

- [1] Yang H, Chen X, Huang G, et al., Microstructures and mechanical properties of titanium-reinforced magnesium matrix composites: Review and perspective. *J. Magnes. Alloy.* 2022, 10(9): 2311-2333.
- [2] V K, Kumar B N, Kumar S S, et al., Magnesium role in additive manufacturing of biomedical implants – Challenges and opportunities. *Addit. Manuf.* 2022, 55(102802).
- [3] Yang Y, Xiong X, Chen J, et al., Research advances in magnesium and magnesium alloys worldwide in 2020. *J. Magnes. Alloy.* 2021, 9(3): 705-747.
- [4] Li K, Ji C, Bai S, et al., Selective laser melting of magnesium alloys: Necessity, formability, performance, optimization and applications. *Journal of Materials Science & Technology.* 2023, 154: 65-93.
- [5] Wang Y-b, Ma B-q, Wang J-x, et al., Quantitative analysis of columnar-to-equiaxed transition in Mg-Gd-Zn alloys. *China Foundry.* 2025, 22(3): 239-251.
- [6] Yang Y-H, Guan Z-P, Ma P-K, et al., Wire arc additive manufacturing of a novel ATZM31 Mg alloy: Microstructure evolution and mechanical properties. *J. Magnes. Alloy.* 2023,
- [7] Fang X, Yang J, Jiang X, et al., Wire-arc directed energy deposited high-performance AZ31 magnesium alloy via a novel interlayer hammering treatment. *Materials Science and Engineering: A.* 2024, 889.
- [8] Liu W, Jia H-L, Zha M, et al., Superior strength-ductility synergy achieved in WA-DED Mg alloys by modulating precipitates through double-stage aging. *Scr. Mater.* 2025, 267.
- [9] Li X, Fang X, Zhang Z, et al., Revealing precipitation behavior and mechanical response of wire-arc directed energy deposited Mg-Gd-Y-Zr alloy by tailoring aging procedures. *Int. J. Extreme Manuf.* 2024, 6(4).
- [10] Li X, Fang X, Fang D, et al., On the excellent strength-ductility synergy of wire-arc directed energy deposited Mg-Gd-Y-Zn-Zr alloy via manipulating precipitates. *Addit. Manuf.* 2023, 77.
- [11] Han S, Zielewski M, Martinez Holguin D, et al., Optimization of AZ91D Process and Corrosion Resistance

- Using Wire Arc Additive Manufacturing. Appl. Sci. 2018, 8(8):
- [12] Li X, Zhang M, Fang X, et al., Improved strength-ductility synergy of directed energy deposited AZ31 magnesium alloy with cryogenic cooling mode. Virtual. Phys. Prototyp. 2023, 18(1).
- [13] Guo Y, Quan G, Jiang Y, et al., Formability, microstructure evolution and mechanical properties of wire arc additively manufactured AZ80M magnesium alloy using gas tungsten arc welding. J. Magnes. Alloy. 2021, 9(1): 192-201.
- [14] Ma P, Wang C, Jia H, et al., Simultaneous enhancement in deposition efficiency and nano-scale precipitation of high-strength AZ31 Mg alloy via water cooling assisted wire-arc directed energy deposition. Thin-Walled Struct. 2025, 206.
- [15] Yi H, Wang Q, Zhang W, et al., Wire-arc directed energy deposited Mg-Al alloy assisted by ultrasonic vibration: Improving properties via controlling grain structures. J. Mater. Process. Technol. 2023, 321.
- [16] Li X, Fang X, Zhang M, et al., Gradient microstructure and prominent performance of wire-arc directed energy deposited magnesium alloy via laser shock peening. Int. J. Mach. Tools Manuf. 2023, 188.
- [17] Yang Y-H, Jia H-L, Wang C, et al., An innovative strategy to prepare fine-grained Mg-Al alloys with a superior strength-ductility synergy via wire-arc directed energy deposition. Addit. Manuf. 2024, 86.
- [18] Liu M, Liu R, Long J, et al., Influence of oscillating laser on forming characteristics and molten pool flow behavior of aluminum alloy double-wire additive manufacturing. J. Laser Appl. 2023, 35(2).
- [19] Chen C, Wang C, Yang J, et al., Enhanced strength-ductility synergy by promoting columnar-to-equiaxed transition and martensitic microstructure refinement with different laser oscillating strategies. J. Manuf. Process. 2024, 125: 164-175.
- [20] Yu H, Xin Y, Wang M, et al., Hall-Petch relationship in Mg alloys: A review. Journal of Materials Science & Technology. 2018, 34(2): 248-256.
- [21] Zhang Z, Xie J, Zhang J, et al., Towards designing high mechanical performance low-alloyed wrought magnesium alloys via grain boundary segregation strategy: A review. Journal of Magnesium and Alloys. 2024, 12(5): 1774-1791.